

Observation of dc voltage on segments of an inhomogeneous superconducting loop

S. V. Dubonos, V. I. Kuznetsov, and A. V. Nikulov

Institute of Microelectronics Technology and High Purity Materials, Russian Academy of Sciences, 142432 Chernogolovka, Moscow District, RUSSIA

In order to verify a possibility of a dc voltage predicted on segments of an inhomogeneous superconducting loop the Little-Parks oscillations are investigated on symmetrical and asymmetric Al loops. The amplitude of the voltage oscillations ΔV measured on segments of symmetrical loop increases with the measuring current I_m and $\Delta V = 0$ at $I_m = 0$ in accordance with the classical Little-Parks experiment. Whereas the ΔV measured on segments of asymmetric loop has a maximum value at $I_m = 0$. The observation of the dc voltage at $I_m = 0$ means that one of the loop segments is a dc power source and others is a load. The dc power can be induced by both thermal fluctuation and a external electric noise.

PACS numbers: 74.20.De, 73.23.Ra, 64.70.-p

Recently thought-provoking claims were made about violation of the second law of thermodynamics in the quantum regime [1–3]. These claims were made independently by three research teams from different lands and are concerned to different branches of knowledge such as quantum thermodynamics, biomolecules, superconductivity and others. The publication of such sensation statement has attracted the attention of the scientific press [4] but most scientists still are not buying [5] the theoretical arguments presented in [1–3].

The present work is devoted to the experimental verification of a theoretical result [6] according to which a dc voltage can be observed on segments of a inhomogeneous superconducting loop at $T \approx T_c$ without any external current. The value and sign of this dc voltage depend in a periodic way on a magnetic flux Φ within the loop $\overline{V_{os}}(\Phi/\Phi_0)$. The work [6] was provoked by an experimental observation [7] which is not published up to now, however. According to the opinion [3] by one of the authors of the present and [6] works the existence of the dc voltage contradicts to the second law if $\overline{V_{os}}(\Phi/\Phi_0)$ is induced by the thermal fluctuations in the thermodynamic equilibrium state.

In order to verify the result [6] we used the mesoscopic Al structures, one of them is shown on Fig.1. These microstructures are prepared using an electron lithograph developed on the basis of a JEOL-840A electron scanning microscope. An electron beam of the lithograph was controlled by a PC, equipped with a software package for proximity effect correction "PROXY". The exposition was made at 25 kV and 30 pA. The resist was developed in MIBK: IPA = 1: 5, followed by the thermal deposition of a high-purity Al film 60 nm and lift-off in acetone. The substrates are Si wafers. The measurements are performed in a standard helium-4 cryostat allowing us to vary the temperature down to 1.2 K. The applied magnetic field, which is produced by a superconducting coil, never exceeded 35 Oe. The voltage variations down to 0.05 μV could be detected.

We have investigated the dependencies of the dc voltage V on the magnetic flux $\Phi \approx BS$ of some round loops with a diameter $2r = 1, 2$ and $4 \mu m$ and a linewidth

$w = 0.2$ and $0.4 \mu m$ at the dc measuring current I_m and different temperature closed to T_c . Here B is the magnetic induction produced by the coil; $S = \pi r^2$ is the area of the loop. The sheet resistance of the loops was equal approximately $0.5 \Omega/\square$ at 4.2 K, the resistance ratio $R(300K)/R(4.2K) \approx 2$ and the midpoint of the superconducting resistive transition $T_c \approx 1.24 K$. All loops exhibited the anomalous features of the resistive dependencies on temperature and magnetic field which was observed on mesoscopic Al structures in some works [8,9] before. We assume that these features can be connected with big value of the Al superconducting coherence length which can exceed a structure size near T_c .

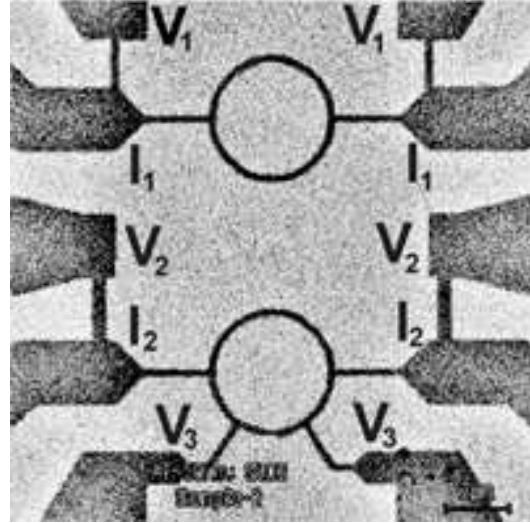


FIG. 1. An electron micrograph one of the aluminum loop samples. I_1 and V_1 are the current and potential contacts of the symmetrical loop. I_2 and V_2 are the current and potential contacts of the asymmetric loop. V_3 are the additional potential contacts of the asymmetric loop.

According to [6] the dc voltage can observed in a inhomogeneous loop and should not observed in a homogeneous one. In order to investigate the influence of the

heterogeneity of loop segments we made both symmetrical and asymmetric loops in each investigated structure (see Fig.1). Because of the additional potential contacts the higher and lower segments of the lower loop (on Fig.1) can have a different resistance at $T \simeq T_c$ when the magnetic flux Φ contained within a loop is not divisible by the flux quantum $\Phi_0 = \pi\hbar c/e$, i.e. $\Phi \neq n\Phi_0$, whereas the one of the higher loop should have the same resistance if any accidental heterogeneity is absent.

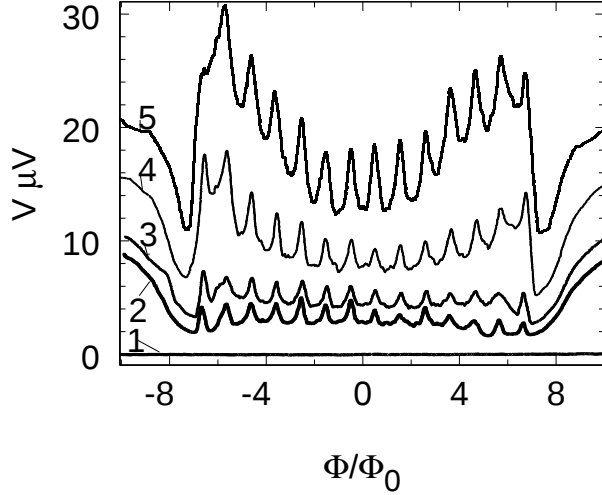


FIG. 2. The voltage oscillations measured on the V_1 contacts of the symmetrical loop with $2r = 4 \mu\text{m}$ and $w = 0.2 \mu\text{m}$ at different I_m values between the I_1 contacts: 1 - $I_m = 0.000 \mu\text{A}$; 2 - $I_m = 1.83 \mu\text{A}$; 3 - $I_m = 2.10 \mu\text{A}$; 4 - $I_m = 2.66 \mu\text{A}$; 5 - $I_m = 3.01 \mu\text{A}$. $T = 1.231\text{K}$ is corresponded to the bottom of the resistive transition

The voltage oscillations measured on the V_1 contacts Fig.2 and on the V_2 contacts Fig.3 confirm qualitative difference between the symmetrical and asymmetric loops. In the first case the amplitude ΔV of the voltage oscillations increases with the measuring current I_m and the oscillations are not observed at $I_m = 0$. Whereas in the second case the greatest oscillations are observed at $I_m = 0$ and the ΔV value does not increase with the I_m , Fig.3. Not only the voltage value but also the sign of the voltage are changed with the magnetic field at $I_m = 0$, Figs.3,4.

In the present work we consider only the region $|\Phi/\Phi_0| < 7$ where the dependencies $V \approx R_m(\Phi/\Phi_0, T/T_c(I_m))I_m$ Fig.2 corresponds to the classical Little-Parks (LP) experiment [10]. The anomalous behaviour, the downfall observed before the disappearance of the oscillation Fig.2, will be considered later. In contrast to the classical LP experiment no resistance but voltage oscillations are observed on the asymmetric loop: $V \approx V_{os}(\Phi/\Phi_0) + R_{nos}I_m$ Fig.3. The resistance R_{nos} depends faintly on I_m and on the magnetic field at low I_m Fig.3. At a high I_m value the negative magnetoresistance R_{nos} is observed Fig.3. Such anomaly was observed also

on other our loops and in other works [9].

According to the universally recognized explanation [11] the LP resistance oscillations are observed [8] because of the fluxoid quantization [10,12]. The resistance increase at $\Phi \neq n\Phi_0$ is interpreted as a consequence of the T_c decrease at a non-zero velocity of superconducting pairs $v_s \neq 0$: $\Delta R = -(dR(T-T_c)/dT)\Delta T_c \propto (dR/dT)v_s^2$ [11]. Because of the quantization

$$\int_l dl v_s = \frac{\pi\hbar}{m} \left(n - \frac{\Phi}{\Phi_0} \right) \quad (1)$$

the v_s circulation can not be equal zero at $\Phi = BS + LI_s \simeq BS \neq n\Phi_0$ [11]. At zero measuring current the v_s value is proportional to the superconducting screening current $v_s \propto I_{sc} = s2en_s v_s = s2e \langle n_s^{-1} \rangle^{-1} (\pi\hbar/ml)(n - \Phi/\Phi_0)$. $\langle n_s^{-1} \rangle = l^{-1} \int_l dl n_s^{-1}$ is used because the superconducting current $I_s = s j_s = s2en_s v_s$ should be constant along the loop in the stationary state. At $I_m \neq 0$ and $\langle n_s^{-1} \rangle^{-1} \neq 0$ in one of the loop segments $|v_s| \propto |I_m/2 + I_{sc}|$ and in the other one $|v_s| \propto |I_m/2 - I_{sc}|$.

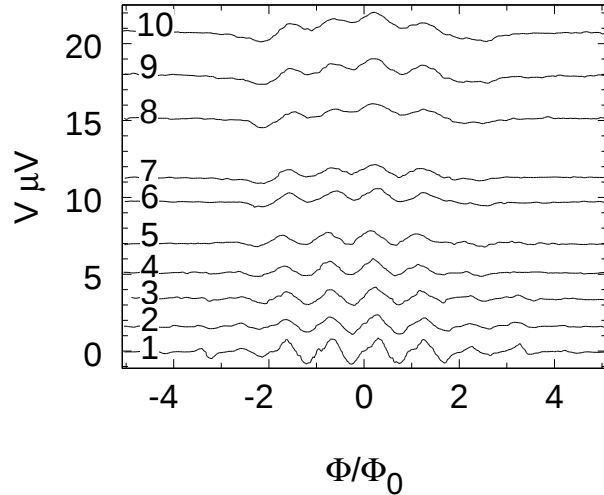


FIG. 3. The voltage oscillation measured on the V_2 contacts of the asymmetric loop with $2r = 4 \mu\text{m}$ and $w = 0.4 \mu\text{m}$ at different value of the measuring current between the I_2 contacts: 1 - $I_m = 0.000 \mu\text{A}$; 2 - $I_m = 0.29 \mu\text{A}$; 3 - $I_m = 0.65 \mu\text{A}$; 4 - $I_m = 0.93 \mu\text{A}$; 5 - $I_m = 1.29 \mu\text{A}$; 6 - $I_m = 1.79 \mu\text{A}$; 7 - $I_m = 2.06 \mu\text{A}$; 8 - $I_m = 2.82 \mu\text{A}$; 9 - $I_m = 3.34 \mu\text{A}$; 10 - $I_m = 3.85 \mu\text{A}$. $T = 1.231\text{K}$ is corresponded to the bottom of the resistive transition

Because $I_{sc} = 0$, $R_{hs} \neq 0$ or/and $R_{ls} \neq 0$ at $\langle n_s^{-1} \rangle^{-1} = 0$ when any loop segment in the normal state, i.e. the density of superconducting pairs $n_s = 0$, and $R_{hs} = 0$, $R_{ls} = 0$ at $\langle n_s^{-1} \rangle^{-1} \neq 0$ when the whole loop is in the superconducting state, i.e. $n_s \neq 0$ along the whole loop, the LP oscillations are observed only near T_c where the switching between the states with $\langle n_s^{-1} \rangle^{-1} \neq 0$ and $\langle n_s^{-1} \rangle^{-1} = 0$ take place and the I_{sc} , R_{hs} , R_{ls} values change in time. Here R_{hs} and R_{ls} are the resistance of the higher and lower segments in

a stationary state. The resistance $R_m = V/I_m$ and the voltage V measured at the LP experiment are the average in time values: $V = \overline{V(t)} = t_{long}^{-1} \int_{t_{long}} dt V(t)$; $R_m \approx \overline{(1/R_{hs} + 1/R_{ls})^{-1}} = \sum P(R_{hs}, R_{ls}) (1/R_{hs} + 1/R_{ls})^{-1}$. Where $P(R_{hs}, R_{ls})$ is the probability of the states with non-zero R_{hs} and R_{ls} values.

According to [11] not only the average $\overline{I_{sc}^2} = t_{long}^{-1} \int_{t_{long}} dt I_{sc}^2$ but also $\overline{s j_{sc}} = \overline{I_{sc}} = t_{long}^{-1} \int_{t_{long}} dt I_{sc} \approx s 2e < n_s^{-1} >^{-1} (\pi \hbar / m l) (n - \Phi / \Phi_0)$ is not equal zero at $\Phi \neq n \Phi_0$ and $\Phi \neq (n + 0.5) \Phi_0$. The theoretical dependence $\Delta T_c \propto -(n - \Phi / \Phi_0)^2_{min}$, where n is corresponded to minimum possible value $v_s^2 \propto (n - \Phi / \Phi_0)^2$ [11] describes enough well the experimental data (see for example Fig.4 in [8]). Therefore $(n - \Phi / \Phi_0) \approx (n - \Phi / \Phi_0)_{min}$ when Φ is not close to $(n + 0.5) \Phi_0$. $\overline{I_{sc}} = 0$ at $\Phi = (n + 0.5) \Phi_0$ because the permitted states with opposite v_s direction have the same v_s^2 value. Thus, the LP experiment is evidence of the persistent screening current $I_{p.c.} = \overline{I_{sc}}$ flows along the loop at a constant magnetic flux, $\Phi \neq n \Phi_0$ and $\Phi \neq (n + 0.5) \Phi_0$, and $R_l \neq 0$.

It is enough obvious from the analogy with a conventional loop that the potential difference $\overline{V_{sc}} = (\langle \overline{\rho} >_{l_s} - \langle \overline{\rho} >_{l_s} \rangle) l_s \overline{j_{sc}}$ can be observed on a segment l_s of an inhomogeneous loop at $\overline{j_{sc}}$ if the average resistivity along the segment $\langle \overline{\rho} >_{l_s} = \int_{l_s} dl \overline{\rho} / l_s$ differs from the one along the loop $\langle \overline{\rho} >_l = \int_l dl \overline{\rho} / l$. Because the $\overline{I_{sc}}(\Phi / \Phi_0)$ oscillations take place both in the symmetrical and asymmetric loops the absence of the voltage oscillations at $I_m = 0$ on the contacts V_1 Fig.2 and the observation on V_2 Figs.3,4 mean that $\overline{R_{hs}} = \overline{R_{ls}}$ in the first case and $\overline{R_{hs}} \neq \overline{R_{ls}}$ in the second case. The later can be if the critical temperature of the higher and lower segments are different: if $T_{ch}(\Phi) \neq T_{cl}(\Phi)$ then $\overline{R_{hs}}(T - T_{ch}) \neq \overline{R_{ls}}(T - T_{cl})$ at $T \approx T_{ch}, T_{cl}$.

Consequently, the voltage oscillations at $I_m = 0$ Fig.3,4 can be caused by the superconducting screening current, as well as the LP oscillations Fig.2. The comparison of the experimental data for symmetrical and asymmetric loops confirms this supposition. Our investigations have shown that the voltage oscillations as well as the LP oscillations were observed only in the temperatures corresponded to the resistive transition. Both oscillations have the same period. The magnetic field regions, where they are observed, are also closed.

The oscillations on Fig.2 are observed in more wide magnetic field region than on Figs.3,4 because the width of the wire defining the loop in the first case $w = 0.2 \mu m$ is smaller than in the second case $w = 0.4 \mu m$. In any real case only some oscillations are observed because a high magnetic field breaks down the superconductivity, i.e I_{sc} , in the wire defining the loop and the contact grounds. According to (1) $v_s = (\pi \hbar / m) B r / 2$ along the loop and $v_s = (\pi \hbar / m) B w / 2$ along the boundaries of the wire at $n = 0$. Therefore a limited number of oscillations $\propto 2r/w$ are observed. The wide contact grounds, with the width $\approx 2 \mu m$ (see Fig.1), have also an influence on the

oscillation number.

According to the analogy with a conventional loop the voltage measured between the V_2 contacts $\overline{V_{sc}} = 0.5(\overline{R_{hs}} - \overline{R_{ls}}) \overline{I_{sc}}$ and consequently the voltage oscillations with the amplitude $\Delta V \approx 1 \mu V$ observed on Fig.4 can be induced by $\overline{I_{sc}}$ oscillations with $\Delta \overline{I_{sc}} \geq 0.4 \mu A$ because $\overline{R_{hs}}, \overline{R_{ls}} \leq R_{ln} / 2 = 5 \Omega$. The screening current $|\overline{I_{sc}}|$ inducing the R_m oscillations Fig.2 can be evaluate from the experimental data if the $dR_m/d|\overline{I_{sc}}|$ value is known. Although $|I_m/2 + I_{sc}| > |I_m/2|$ in one of the segments and $|I_m/2 - I_{sc}| < |I_m/2|$ in the other one at $|I_m/2| > |I_{sc}|$ $dR_m/d|\overline{I_{sc}}| > 0$ and the LP oscillations are observed at both small and large I_m (see Fig.2 and [8]) because I_{sc} , as well I_m , decreases the probability of superconducting state $< n_s^{-1} >^{-1} \neq 0$ and consequently increases the $P(R_{hs} \neq 0, R_{ls} \neq 0)$. If one assumes that the $dR_m/d|I_m|$ and $dR_m/d|\overline{I_{sc}}|$ are closed in order of value then according to the data presented on Fig.2 $|\overline{I_{sc}}| \approx 0.4 \mu A$ at $\Phi = (n + 0.5) \Phi_0$.

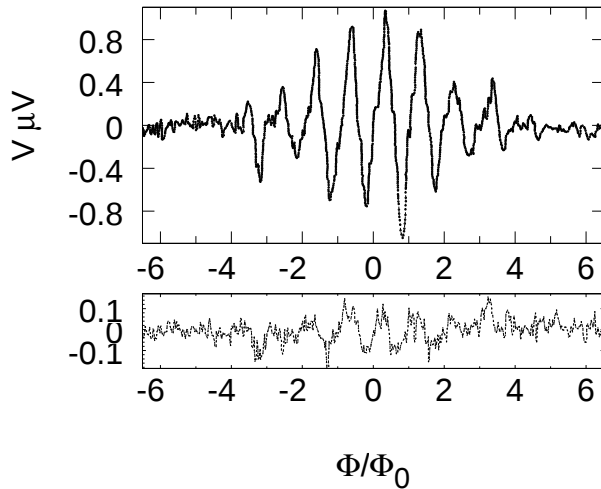


FIG. 4. Oscillation of the voltage measured on the V_2 contacts (upper curve) and on the V_3 contacts (lower curve) of the asymmetric loop with $2r = 4 \mu m$ and $w = 0.4 \mu m$. $I_m = 0$. $T = 1.231 K$ corresponded to the bottom of the resistive transition.

Thus, the analogy with a conventional loop and the classical LP experiment Fig.2 explain enough well the voltage oscillations observed at $I_m = 0$ Figs.3,4. But in contrast to the case of the conventional loop when the current $I_{sc} = R_l(-1/c)d\Phi/dt$ and the electric field $E = -\nabla V - (1/c)dA/dt = -\nabla V - (1/cl)d\Phi/dt$ have the same direction in both segment in our case $d\Phi/dt = 0$ and consequently the average current $\overline{I_{sc}}$ and the average electric field $\overline{E} = -\nabla V$ should have opposite directions in one of the segments because $\int_l dl \nabla V \equiv 0$. This means that one of the loop segments is a dc power source $W = \overline{V_{os}} \overline{I_{sc}}$ and others is a load.

The existence of the dc power contradicts to some habitual knowledge if W is not induced by a temperature

difference ΔT . The voltage oscillations Fig.4 can be explain by an accidental temperature difference $V_{os} = S_{th}\Delta T$ only if the thermopower S_{th} is oscillated and its sign is switched together with the $\overline{I_{sc}}$. The thermopower oscillations are observed in some Andreev interferometer [13] but its value is very small in order to explain the voltage oscillations observed in our work.

Because the voltage and LP oscillations are observed in the same region it is naturally to explain the observation of the dc power as a direct consequence of the contradiction of the LP experiment with the Ohm's law $R_l I_{sc} = \int_l dl E = -(1/c)d\Phi/dt$ and other fundamental laws [14]. The existence of $\overline{I_{sc}} \neq 0$ at $\overline{R_l} \neq 0$ and $d\Phi/dt = 0$ is explained [14] by the change of the momentum circulation of superconducting pairs from $\int_l dl p = \int_l dl (2mv_s + (2e/c)A) = (2e/c)\Phi$ at $< n_s^{-1} >^{-1} = 0$ to $\int_l dl p = n2\pi\hbar$ at $< n_s^{-1} >^{-1} \neq 0$ at the closing of superconducting state, when its connectivity changes.

These momentum changes because of the quantization $n2\pi\hbar - (2e/c)\Phi = 2\pi\hbar(n - \Phi/\Phi_0)$ take the place of the Faraday's voltage $-(1/c)d\Phi/dt$. The force maintaining the persistent current, as well as the Faraday's electric field $-(1/cl)d\Phi/dt$, should be uniform along the loop because the momentum change on the unit volume $\Delta P \propto j_s$ [14]. This warrants the analogy with a conventional loop used above.

At a enough low frequency, when the switching takes place between the stationary states

$$\overline{V_{os}} = (\frac{< \bar{\rho} >_{l_s}}{< \bar{\rho} >_l} - 1) \frac{l_s}{l} \frac{\pi\hbar}{e} (n - \frac{\Phi}{\Phi_0}) \omega \quad (2)$$

on a l_s segment. $\omega = N_{sw}/t_{long}$ is the average frequency of a switching between the superconducting state with different connectivity; N_{sw} is the number of switching for t_{long} . The amplitude of the oscillations $\Delta\overline{V_{os}} \leq 0.25(\pi\hbar/e)\omega$ at $l_s = l/2$. $\pi\hbar/e = 2.07 \mu V/GHz$ is equal to the ratio of the voltage and the frequency in the Josephson effect [15]. Consequently, according to (2) the oscillations Fig.4 with $\Delta V \approx 1 \mu V$ can be observed if $\omega \geq 2 GHz$.

The $\Delta\overline{V_{os}}$ increases more slowly with the frequency than (2) if $\omega > 1/\tau_{rel}$. Where τ_{rel} is any relaxation time in stationary states, which can be equal the relaxation time of superconducting fluctuations τ_{fl} [11] or the decay time of the screening current τ_R . $1/\tau_{fl} \approx 2 GHz$ in order of value because $\tau_{fl} = \pi\hbar/8k_B(T - T_c)$ in the linear approximation region above T_c [11] and the width of the critical region of our loops $\Delta T_{r.t.} \approx 0.02K$. $1/\tau_R \approx (2e^2/m)n_s\rho_n \approx e\rho_n\overline{j_{sc}}/mv_s \approx 10 GHz$ in order of value. Here the value $|\overline{j_{sc}}| = |\overline{I_{sc}}|/s \approx 2 \cdot 10^7 A/m^2$ found above, $|v_s| = \pi\hbar/2ml \approx 30 m/s$ for $|n - \Phi/\Phi_0| = 0.5$ and the ρ_n value of Al were used. Consequently, the voltage oscillations observed in our work Fig.3,4 can be induced by a switching between the superconducting state with different connectivity.

This switching can be induced by both the thermal fluctuations and an external electric noise. A high-

frequency noise with $I_{noise} \geq sj_c = (c^2sk_BT/2\pi\lambda^2\xi)^{1/2}$ increases the probability P_{sw} of the switching in the normal state. $P_{sw} \propto \exp(-sl_sf_{sup}/k_BT)$ at $l_s \geq \xi$, where $f_{sup} = (2\pi/c^2)\lambda^2j_c^2$ is the energy density of the transition in the normal state [11]; ξ is the superconducting coherence length; λ is the London penetration depth. For the loops used in our work $(c^2sk_BT/2\pi\lambda^2\xi)^{1/2} \approx (\Delta T_{r.t.}/T_c)^{3/4} 10^{-5} A \approx 0.5 \mu A$. We can not guarantee that $I_{noise} \ll 0.5 \mu A$. Moreover we observed an influence of an external electric noise on the $\overline{V_{os}}$ value. Therefore we can not state that the voltage oscillations observed in our work at $I_m = 0$ are induced in the equilibrium state although the power $W = \overline{V_{os}}\overline{I_{sc}} \approx 2 \cdot 10^{-13} Wt$ does not exceed the limit value $k_BT/\hbar \approx 10^{-12}$ [3,14] which can be induced by the thermal fluctuations.

In conclusion, we have observed voltage oscillations measured on segments of an inhomogeneous loop at zero external direct current in the same region where the Little-Parks oscillations are observed. This voltage can be induced by both thermal fluctuation and an external electric noise.

We acknowledge useful discussions with V.A.Tulin.

-
- [1] A.E.Allahverdyan and Th.M.Nieuwenhuizen, *Phys.Rev.Lett.* **85**, 1799 (2000); cond-mat/0011389
 - [2] V.Capec and J.Bok, *Czech. J. of Phys.* **49**, 1645 (1999); *Physica A* **290**, 374 (2001); V.Capec, cond-mat /0012056
 - [3] A.V.Nikulov, physics/9912022; *Abstracts of XXII International Conference on Low Temperature Physics*, Helsinki, Finland, p.498 (1999); in *Supermaterials*, Eds. R.Cloots et al. Kluwer Academic Publishers, 2000, p.183
 - [4] P.F.Schewe and B.Stein, on <http://www.aip.org/enews/physnews/2000/split/pnu494-1.htm>
 - [5] P. Weiss, *Science News* **158**, 234 (2000).
 - [6] A.V. Nikulov and I.N. Zhilyaev, *J. Low Temp.Phys.* **112**, 227-236 (1998).
 - [7] I.N. Zhilyaev, private communication (unpublished).
 - [8] H.Vloeberghs et al., *Phys. Rev.Lett.* **69**,1268 (1992).
 - [9] P.Santhanam, C.P.Umbach, and C.C.Chi, *Phys.Rev. B* **40**, 11392 (1989); P.Santhanam et al. *Phys.Rev.Lett.* **66**, 2254 (1991).
 - [10] W.A.Little and R.D.Parks, *Phys. Rev. Lett.* **9**, 9 (1962).
 - [11] M.Tinkham, *Introduction to Superconductivity*. McGraw-Hill Book Company (1975).
 - [12] M.Tinkham, *Phys. Rev.* **129**, 2413 (1963).
 - [13] J.Eom, C.J. Chien, and V.Chandrasekhar, *Phys.Rev. Lett.* **81**, 437 (1998).
 - [14] A.V. Nikulov, *Phys.Rev.B*, July 2001; physics/0104073
 - [15] A.Barone and G.Paterno, *Physics and Application of the Josephson Effect*. A Wiley - Interscience Publication, John Wiley and Sons, New York, 1982